



HAL
open science

Effect of the Plasma Etching on InAsP/InP Quantum Well Structures Measured through Low Temperature Micro-Photoluminescence and Cathodoluminescence

Jean-Pierre Landesman, Nebile Isik Goktas, Ray Lapierre, Shahram Ghanad-Tavakoli, Erwine Pargon, Camille Petit-Etienne, Christophe Levallois, Juan Jiménez, Shabnam Dadgostar

► To cite this version:

Jean-Pierre Landesman, Nebile Isik Goktas, Ray Lapierre, Shahram Ghanad-Tavakoli, Erwine Pargon, et al.. Effect of the Plasma Etching on InAsP/InP Quantum Well Structures Measured through Low Temperature Micro-Photoluminescence and Cathodoluminescence. ECS Transactions, 2020, 97 (2), pp.43-55. 10.1149/09702.0043ecst . hal-02917592

HAL Id: hal-02917592

<https://hal.univ-grenoble-alpes.fr/hal-02917592v1>

Submitted on 18 Nov 2020

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Effect of the Plasma Etching on InAsP/InP Quantum Well Structures Measured Through Low Temperature Micro-photoluminescence and Cathodoluminescence

J. P. Landesman^a, N. Isik Goktas^b, R. R. LaPierre^b, S. Ghanad-Tavakoli^b, E. Pargon^c,
C. Petit-Etienne^c, C. Levallois^d, J. Jiménez^e, and S. Dadgostar^e

^a Univ Rennes, CNRS, IPR - UMR 6251, 35000 Rennes, France

^b Department of Engineering Physics, McMaster University, Hamilton L8S 4L7, Canada

^c Université Grenoble Alpes, CNRS, LTM, 38000 Grenoble, France

^d Univ Rennes, INSA Rennes, CNRS, Institut FOTON—UMR 6082, 35000 Rennes,
France

^e Dpto. Física de la Materia Condensada, Universidad de Valladolid, 47011 Valladolid,
Spain

Photoluminescence and cathodoluminescence spectral imaging were performed across rectangular stripes etched in samples with InAs_xP_{1-x} quantum wells of constant thickness and variable composition grown on InP. In particular, the effects of different etching chemistries (CH₄/H₂/Ar and Cl₂/CH₄/Ar) were investigated. The results discussed deal with modifications of the luminescence line shapes (which differ with etching process) and with the intensity variation of the emissions associated with the quantum wells across the stripes. The possible origins of these effects are investigated in terms of carrier recombination on the vertical sidewalls of the stripes and lateral diffusion of species from the plasma during etching. Cathodoluminescence measurements on samples under DC-bias also show the quantum confined Stark effect which is correlated to the material modifications induced by the etching.

Introduction

Many fabrication processes for photonic devices in III-V semiconductors involve plasma etching, also designated as reactive ion etching (RIE), for the definition of features with anisotropic profile. For example, waveguides in InP-based materials with rectangular profiles are made using this kind of tool (1). However, plasma etching is also a possible source of defects in the material during the process. This issue has already been investigated by a number of groups. The induced disorder can be chemical, e.g. non-stoichiometry (2), crystallographic, e.g. creation of an amorphous layer or collision cascades (2, 3), and/or creating defects that affect the electronic and optical properties (4 – 6). Due to the preferential direction of ions impinging the material, horizontal etched surfaces and vertical sidewalls show different behaviors. Interaction mechanisms with the impinging ions and chemical radicals have been proposed to explain the disorder. Ion channeling and diffusion (5) in particular were suggested to explain disorder occurring at depths of hundreds of nanometers below the etched surface.

Decreasing the As content in the QWs from substrate / buffer to the surface increases the energy band-gap, ensuring that the PL or CL signal from deeper QWs will not be absorbed in the QWs above (see following sub-section).

Some samples were grown without any intentional doping, whereas other samples were grown with Be doping added to the InP buffer and barrier layers (p-type doping level $\sim 10^{18} \text{ cm}^{-3}$).

Etching of Rectangular Ridges

Plasma enhanced chemical vapor deposition of silicon nitride SiN_x was used as the etching mask. This layer was grown at 250 °C with a thickness of 500 nm. Stripes of various widths (1 to 50 μm) were defined by optical lithography in this mask. After mask opening, the etching of the different samples was performed by plasma etching. Two different processes were used:

Process #1: capacitively coupled RIE reactor with $\text{CH}_4/\text{H}_2/\text{Ar}$ gas mixture.

Process #2: inductively coupled RIE reactor with $\text{Cl}_2/\text{CH}_4/\text{Ar}$ gas mixture.

The etch depth was 2 μm to ensure etching of all QWs.

Details for the Etching Process #1: After SiN_x mask opening and resist stripping, the InP etching was done with 6.4 sccm CH_4 / 50 sccm H_2 / 8.4 sccm Ar (total pressure: 30 mTorr), and a power of 40 W. No external sample heating was used.

After etching the InP, the polymer formed during the etching was first etched in the plasma using 50 sccm O_2 (total pressure: 6 mTorr) with a power of 50 W, and the SiN_x mask was subsequently stripped in HF.

Details for the Etching Process #2: After SiN_x mask opening and resist stripping, the InP etching was done using 20 sccm Cl_2 / 100 sccm Ar / 32 sccm CH_4 (total pressure: 20 mTorr), a power of 800 W at the plasma source and 200 W for sample bias, and a sample temperature of 200 °C.

After etching the InP, the SiN_x mask and polymer passivation were first etched in HF and then stripped in the plasma using 90 sccm O_2 (total pressure: 10 mTorr), and a power of 800 W.

μPL Setup

The μPL experiments were performed at 10 K using a specially designed optical cryostat (9). The chosen excitation wavelength was 1064 nm to avoid the generation of electron-hole pairs in the InP substrate, buffer and barrier layers. The excitation power density was approximately 5.107 W/cm^2 . The PL spectrum obtained under these conditions for an as-grown un-doped sample with 8 QWs, prior to etching, is shown in figure 2.

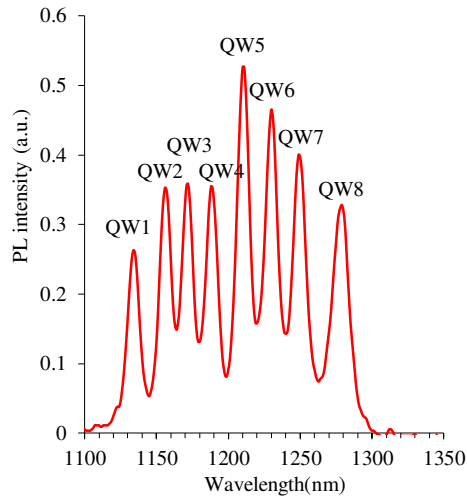


Figure 2. Low temperature (10 K) PL spectrum of an un-doped sample after growth (8 QWs). The lines are labeled with the QW number in the structure.

CL Setup

The CL spectral images were recorded in a Carl Zeiss (LEO 1530) field emission scanning electron microscope, equipped with a Gatan mono-CL2 system with a liquid nitrogen - cooled InGaAs array detector. These measurements were done on cooled samples (80 K). The acceleration voltage for the electron gun was set to 20 kV. The penetration depth for this voltage is in the order of 1 μm (10). A typical CL spectrum obtained for an as-grown, un-doped sample can be seen in figure 3.

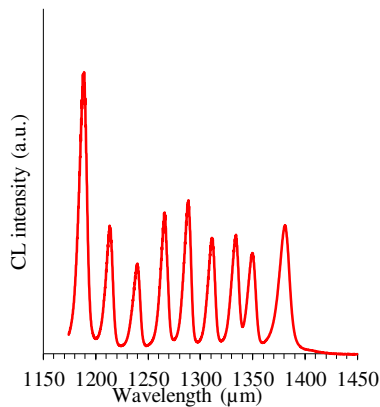


Figure 3. CL spectrum (80 K) of an un-doped sample after growth (9 QWs).

Experimental Results

As-grown Samples

We first comment on the spectra measured for the as-grown samples, before any etching process, such as shown in figs. 2 and 3. The signature of each QW can clearly be identified. The peaks are sharp (spectral width on the PL spectra at 10 K: 4.5 nm /

4.4 meV for the sharpest transition). These spectra display for each line a single, symmetric transition, indicating that a single hole level is apparently confined in the QWs due to compressive stress. A very good fit to the experimental PL spectra is obtained using Gaussian profiles for each line, with adjustable position, amplitude and width, as illustrated in figure 4.

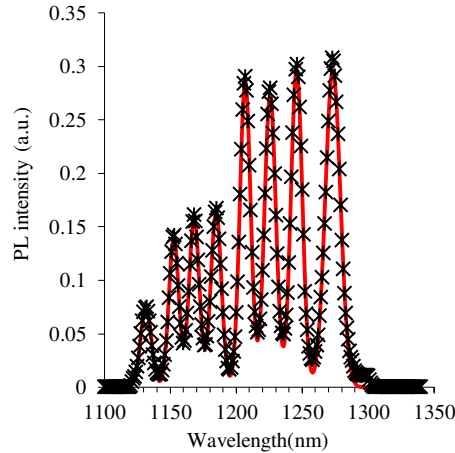


Figure 4. Low temperature (10 K) PL spectrum. * indicates measured data and red lines indicate the model fit.

Doping leads to a significant broadening of the emission lines (fig. 5).

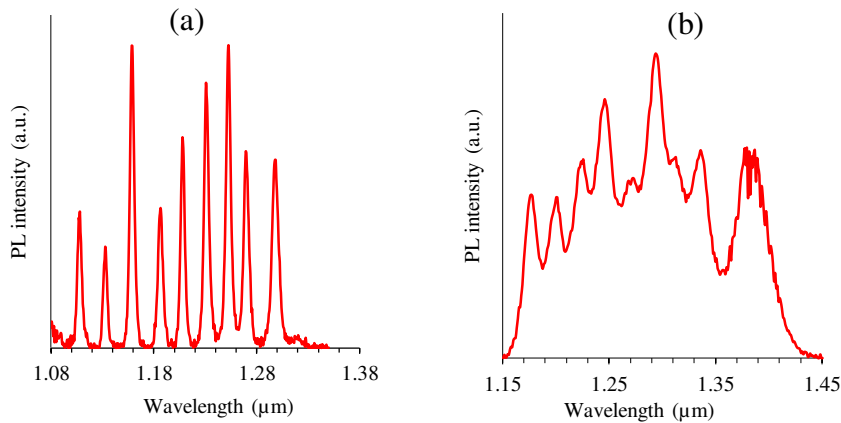


Figure 5. Low temperature (10 K) PL spectrum of (a) un-doped sample; (b) doped sample. Both samples have the same epitaxial structure with 9 QWs, except for the Be-doping in the InP barriers in the case of the doped sample.

This broadening effect is most probably due to a transfer of the carriers in the InP barriers due to Be doping into the $\text{InAs}_x\text{P}_{1-x}$ QWs. Because of this transfer, a range of energy levels in the valence band becomes populated by holes. Under photo-pumping, the electrons created can recombine with holes in this entire range, thus broadening the PL signal (11).

CL spectra at 80 K yield similar trends as the PL spectra for the reference un-etched samples (8).

PL Spectral Imaging on Etched Samples

We now examine the spectral images produced by scanning the laser beam across etched stripes at 10 K in the μ PL set-up. Raw data obtained for stripes (width: $W = 50 \mu\text{m}$) etched using the different processes are displayed in figure 6.

The spectra in figure 6 were recorded on stripes etched from un-doped samples. The corresponding reference spectrum is shown in figure 2. Each spectrum was fitted with the model curve described above. Comparing with the reference spectrum, the following statements can be done:

- the $\text{CH}_4/\text{H}_2/\text{Ar}$ process increases the spectral line width (average line width: 7 nm)
- the $\text{Cl}_2/\text{CH}_4/\text{Ar}$ process slightly decreases the spectral line width (sharpest lines: 3.8 nm)

Fitting with the model curve also allows plotting the intensity variation for each line versus position of the laser beam across the stripes. Examples of intensity variations are shown in figure 7 for two different stripes (widths 30 and 50 μm respectively) etched with the $\text{CH}_4/\text{H}_2/\text{Ar}$ process. The $\text{Cl}_2/\text{CH}_4/\text{Ar}$ process gives similar trends for the intensity distribution across the stripes. The main information derived from the intensity variation curves is the gradual decrease on both edges, extending over more than 10 μm on each side. A plateau seems to be reached for the case of the 50 μm stripe, but not for the 30 μm stripe.

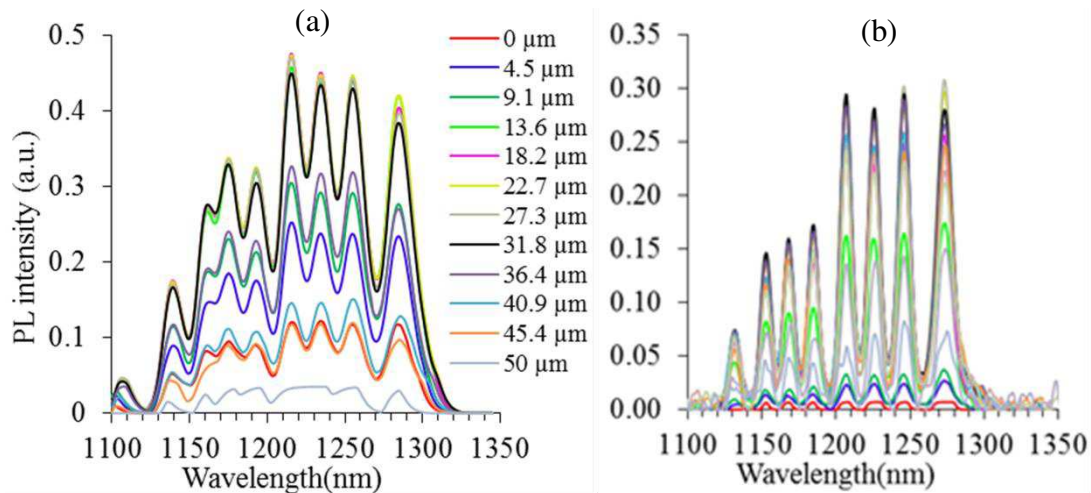


Figure 6. Series of μ PL spectra measured at low temperature (10 K) across 50 μm ridges. (a) etching with $\text{CH}_4/\text{H}_2/\text{Ar}$, and (b) etching with $\text{Cl}_2/\text{CH}_4/\text{Ar}$. Each color corresponds to a different position across the ridge as indicated by the legend in the center. The center of the ridge corresponds to the 25 μm position.

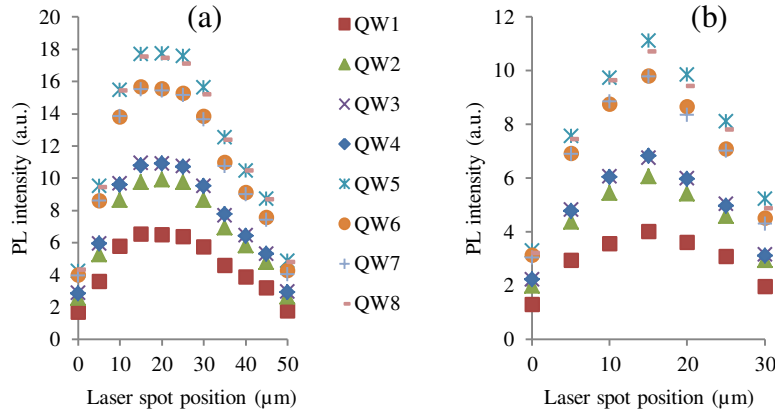


Figure 7. Integrated intensity for individual PL lines across stripes with etch depth 2 μm after the $\text{CH}_4/\text{H}_2/\text{Ar}$ process. (a) Stripe width 50 μm , and (b) stripe width 30 μm .

CL Spectroscopy on DC-Biased Samples

We focus here on the spectroscopic measurements performed in the CL set-up applying a DC bias on the surface of the sample, whereas the backside is grounded. Such measurements were performed only on the un-doped samples for the moment. Figure 8 illustrates the results for both an un-doped and a doped sample comprising 9 QWs. The surface voltage which could be applied varied from one sample to the other, depending on the magnitude of the generated current.

For both negative and positive applied voltage, the emission lines in the un-doped sample have a small red-shift. This red shift is due to the QCSE (12).

For the doped sample, no change is observed for voltages in the interval [- 4 V, +3 V] but as the voltage reaches - 5 V suddenly a strong emission dominates the spectrum. This emission is associated with QW 9, the closest QW to the InP buffer, i.e. in the zone where the p-n junction was created in the p-doped samples. With a negative bias on the surface of this sample a strong reverse situation is created, probably leading to a depletion of the minority carriers generated in the QWs closer to the surface.

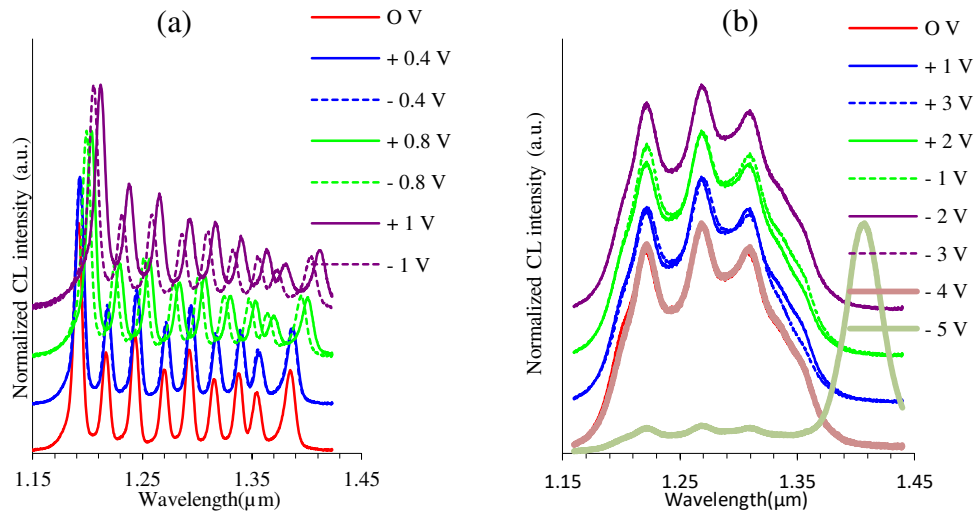


Figure 8. CL spectra recorded at 80 K on samples DC-biased on the surface (9 QWs). (a) un-doped sample, and (b) doped sample. The spectra for different biases were vertically offset for clarity.

In order to better visualize the QCSE induced shifts of the QW lines for the un-doped sample, figures 9 and 10 give a 3-dimensional representation of the CL spectra under DC bias.

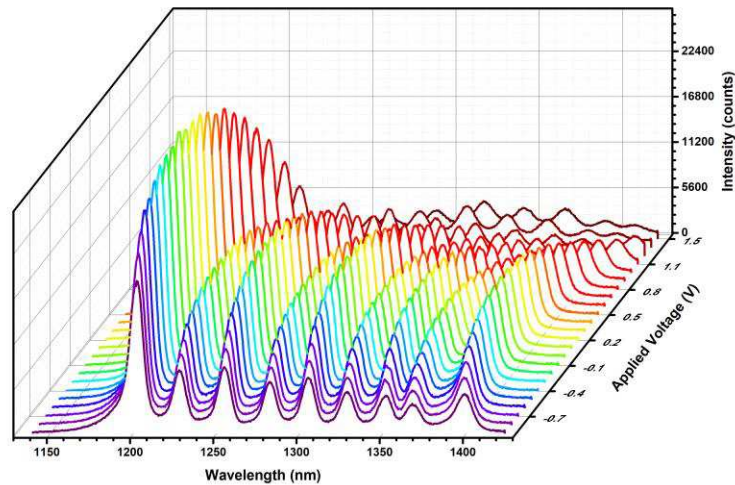


Figure 9. CL spectra measured at 80 K on the un-doped sample as a function of surface DC bias (- 0.9 to 1.5 V applied on the surface in steps of 0.1 V).

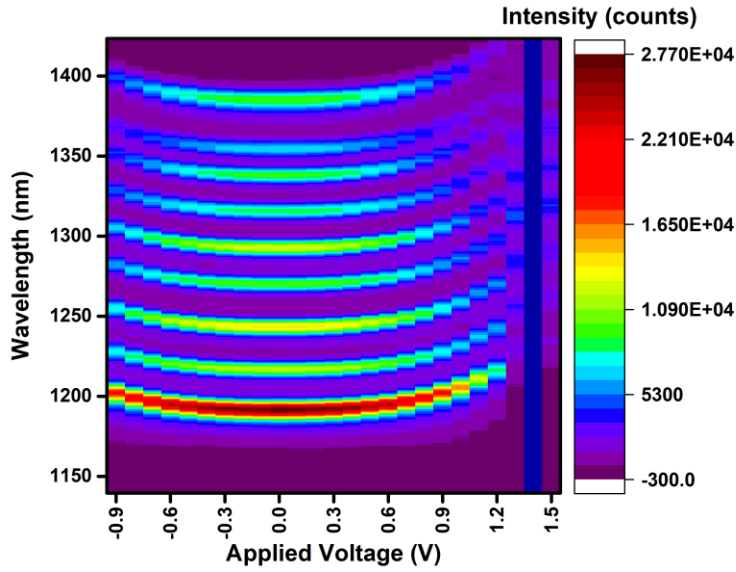


Figure 10. Color map of the CL spectra shown in fig. 8.

Discussion

We first discuss the changes observed on the PL spectra upon etching with the different processes for the un-doped samples. Analyzing the results for the doped samples, however, was more difficult because of the line broadening.

The spectral positions for the different QWs in etched stripes are shown in figure 11 (same sample as figure 7).

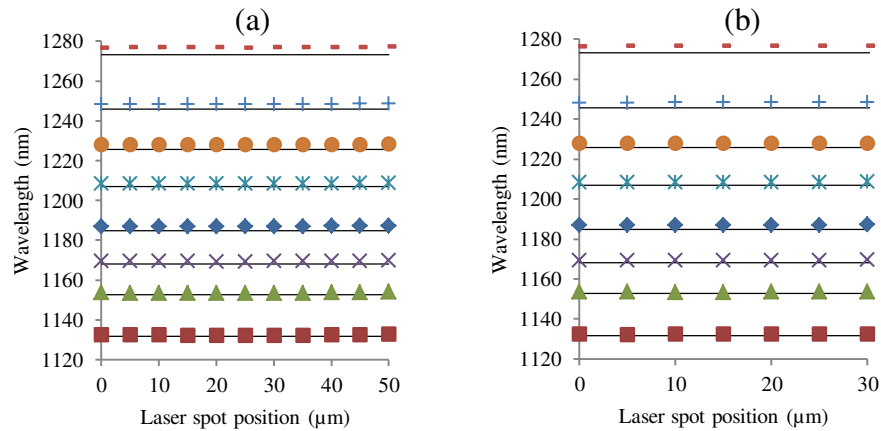


Figure 11. Spectral positions for individual PL lines across stripes with etch depth 2 μm after the $\text{CH}_4/\text{H}_2/\text{Ar}$ process. The straight lines represent the corresponding positions on the reference, un-etched, sample. (a) Stripe width 50 μm , and (b) stripe width 30 μm .

Comparison with the line positions on the reference sample yields the red shifts as indicated in table I.

TABLE I. Spectral shifts measured for the etched stripes (CH₄/H₂/Ar etching process).

QW #	Stripe width 50 μm	Stripe width 30 μm
1	0.8 ± 0.1 nm	0.8 ± 0.1 nm
2	0.9 ± 0.1 nm	0.8 ± 0.1 nm
3	1.3 ± 0.1 nm	1.2 ± 0.1 nm
4	2.2 ± 0.1 nm	2.2 ± 0.1 nm
5	1.7 ± 0.1 nm	1.6 ± 0.1 nm
6	2.3 ± 0.1 nm	2.2 ± 0.1 nm
7	2.6 ± 0.1 nm	2.5 ± 0.1 nm
8	3.6 ± 0.1 nm	3.3 ± 0.1 nm

There is a significant trend towards increasing red shift for QWs located deeper in the sample (with an exception for QW5). On the other hand, the spectral positions are remarkably constant across the stripes, contrary to line intensities (figure 7).

The line intensities show strong variations across the etched stripes. We tried fitting using a function with the form:

$$A \left(1 - \text{Bexp} \left(-\frac{x}{L} \right) - \text{Bexp} \left(\frac{x-W}{L} \right) \right) \quad [1]$$

where A represents the PL signal which should be measured in an area not affected by the presence of the stripe edges, x the position along the stripe, W the stripe width, L the minority carrier diffusion length, and B a term that depends on the surface recombination velocity on the etched vertical walls (13, 14). More precisely, B has the form $B = \frac{S}{S+1}$ where $S = \frac{sv_v \tau}{L}$. sv_v is the surface recombination velocity on the vertical etched walls, τ the radiative lifetime, and S is called the reduced surface recombination velocity. The resulting fits are shown on figure 12 for a 30 μm stripe etched with the CH₄/H₂/Ar process (same sample as figure 7).

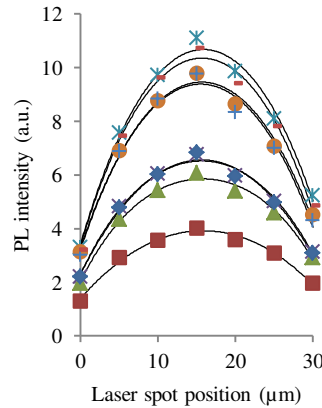


Figure 12. Curve fitting and experimental QW line intensities across a 30 μm stripe with etch depth 2 μm after the CH₄/H₂/Ar process. The symbols have the same meaning as in figure 7.

The parameters resulting from this fitting procedure are given in table II below.

TABLE II. Fitting parameters for PL line intensities measured on the 30 μm stripe ($\text{CH}_4/\text{H}_2/\text{Ar}$ etching process).

QW #	A	B	S (reduced surface recombination velocity)	L (μm)
1	13.3	0.72	2.57	22
2	8.4	0.72	2.57	10
3	10.7	0.73	2.7	11.8
4	18.5	0.73	2.7	19
5	24	0.76	3.17	15.8
6	22.5	0.74	2.85	16.7
7	18.9	0.74	2.85	14.3
8	20.5	0.75	3.0	14.1

The best fit curves agree reasonably well with the experimental data. Assuming the same diffusion length for all QWs, we get $L = 15 \pm 3 \mu\text{m}$. This value indicates that the QWs have a very high quality and have not been degraded by the etching process. The reduced surface recombination velocity appears rather constant for all QWs (2.8 ± 0.2). Determination of the true surface recombination velocity requires measurement of the radiative life time.

We applied the same fitting procedure for the 50 μm stripe of figure 7-a. Only the left half of the stripe was used for the fitting procedure as the right half shows some irregular behavior. The curve fitting is shown in figure 13, and the corresponding fitting parameters in table III. The diffusion length for this stripe is about half the diffusion length found for the 30 μm stripe, and the reduced surface recombination velocity is 30 % higher than found for the 30 μm stripe. We do not really have an explanation for this, as both stripes were etched during the same process. However, the results show the interest of the measurement methodology based on the μPL set-up at low temperature for the evaluation of the impact of the plasma etching process on the material's parameters.

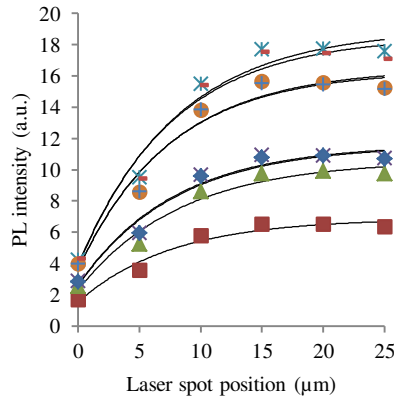


Figure 13. Curve fitting and experimental QW line intensities across a 50 μm stripe (left edge) with etch depth 2 μm after the $\text{CH}_4/\text{H}_2/\text{Ar}$ process. The symbols have the same meaning as in figure 7.

TABLE III. Fitting parameters for PL line intensities measured on the 50 μm stripe ($\text{CH}_4/\text{H}_2/\text{Ar}$ etching process).

QW #	A	B	S (reduced surface recombination velocity)	L (μm)
1	6.9	0.78	3.55	7.7
2	10.6	0.78	3.55	8.3
3	11.6	0.78	3.55	7.8
4	11.6	0.78	3.55	7.9
5	19.0	0.8	4	8
6	16.5	0.78	3.55	7.6
7	16.3	0.78	3.55	7.5
8	18.5	0.79	3.76	7.7

The bias-dependent CL spectra have shown that the QCSE can significantly affect the spectral positions and even line shapes in these samples. The next step will be to simulate this effect and evaluate if the penetration of some species from the etching plasma, for example ions formed either in the plasma phase or within the material as the stable form of these species, might affect the PL and CL spectra. This might, in particular, explain the changes in PL line shapes observed for the 2 different etching processes.

Conclusion

The μPL and CL spectroscopic measurements performed on InAsP/InP QW samples before and after plasma etching processes prove useful to evaluate the impact of the etching on some of the important parameters. These parameters are, in particular, the surface recombination velocity and the charge carrier diffusion length. Evaluating these parameters is important when fabricating such devices as photonic waveguides.

Acknowledgments

The authors would like to thank the Center for Emerging Device Technologies (CEDT) at McMaster University where epitaxial growth was performed. The authors also thank RENATECH+ (the French national network of facilities for micro-nano-technology) with NanoRennes and the LTM etching platform in Grenoble.

References

1. N. P. Siwak, X. Z. Fan, and R. Ghodssi, *J. Micromech. Microeng.*, **25**, 043001 (2015).
2. T. R. Hayes, U. K. Chakrabarti, F. A. Baiocchi, A. B. Emerson, H. S. Luftman, and W. C. Dautremont-Smith, *J. Appl. Phys.*, **68**(2), 785 (1990).
3. J. Etrillard, F. Hélot, P. Ossart, M. Juhel, G. Patriarche, P. Carcenac, C. Vieu, M. Puech, and P. Maquin, *J. Vac. Sci. Technol. A*, **14**(3), 1056 (1996).
4. M. Rahman, *J. Appl. Phys.*, **82**(5), 2215 (1997).
5. D. L. Green, E. L. Hu, P. M. Petroff, V. Liberman, M. Nooney, and R. Martin, *J. Vac. Sci. Technol. B*, **11**, 2249 (1993).
6. C. H. Chen, *J. Vac. Sci. Technol. B*, **14**(6), 3684 (1996).

7. M. Fouchier, M. Fahed, E. Pargon, N. Rochat, J. P. Landesman, D. Rouchon, J. Rocque, K. Rovayaz, E. Martinez, and S. Labau, *MRS Adv.*, **3**,57 (2018).
8. J. P. Landesman, J. Jiménez, C. Levallois, F. Pommereau, C. Frigeri, A. Torres, Y. Léger, A. Beck, and A. Rhallabi, *J. Vac. Sci. Technol. A*, **34**(4), 041304 (2016).
9. C. M. Haapamaki, PhD Dissertation, McMaster University (2012).
10. J. Bonard, J. Ganière, B. Akamatsu, D. Araújo, and F. Reinhart, *J. Appl. Phys.*, **79**(11), 8693 (1996).
11. D. F. Welch, G. W. Wicks, and L. F. Eastman, *Appl. Phys. Lett.*, **46**(10), 991 (1985).
12. L. Vina, E. E. Mendez, W. I. Wang, L. L. Chang, and L. Esaki, *J. Phys. C Solid State Phys.*, **20**(18), 2803 (1987).
13. B. G. Mendis and L. Bowen, *J. Phys. Conf. Ser.*, 326 (2011).
14. W. Van Roosbroeck, *J. Appl. Phys.*, **26**(4), 380 (1955).